



## REACTION TO FIRE CLASSIFICATION REPORT

N° 2014/079-2

(English version of classification report N°2014/079-1)

According to EN 13501-1 (2007) + A1 (2013)

Notification by the French Government to the European Commission  
under n° NB 2401  
Regulation (UE) n° 305/2011

Sponsor : AMTICO INTERNATIONAL SAS  
25 rue de Sèvres  
92100 BOULOGNE  
FRANCE

Product name : AMTICO CLICK SU5W3002 with underlay “UNDERLAY – 19”

Description : polyvinyl chloride floor coverings (EN 649 family)  
(see detailed description in paragraph 2)

Date of issue : 18/11/2014

*The indicated classification does not prejudice the conformity of marketed materials with the samples submitted to the tests and under no circumstances, this document should not be considered as type approval or certification of the product in the sense of the L 115-27 article of the consumption's code of the law dated June 3<sup>rd</sup> 1994.*

*The reproduction of this classification report is only authorised in its integral form.  
It comprise 4 pages*

**1. Introduction**

This classification report defines the classification assigned to the above-mentioned product (s) in accordance with the procedures given in the NF EN 13501-1 standard: September 2007 & A1 (2013).

**2. Details of classified product****2.1. Product standard**

NF EN 14041 (2005): « Resilient, textile and laminate floor coverings - Essential characteristics.

**2.2. Product description**

AMTICO CLICK SU5W3002: Heterogenous polyvinyl chloride floorcovering (EN 649) in size planks LVT.

Use surface: 100 % PVC .

Nominal total mass per unit area : 8400 g/m<sup>2</sup>.

Nominal total thickness : 5,0 mm.

Nominal wear layer thickness: 0,55 mm

Underlay “Underlay – 19”:

Total mass per unit area : 100 g/m<sup>2</sup>.

Total thickness : 5,0 mm.

Nominal density : 100 kg/m<sup>3</sup>

Tested loose laid over a wood panel particle board without flame retarded classified C<sub>fl-s1</sub> with a density (680 ± 50) Kg/m<sup>3</sup> and thickness (20 ± 2) mm.

**3. Test reports and tests results in support of this classification****3.1. Tests reports**

Name of laboratory	Name of sponsor	Test report N°	Test method
C.R.E.T.	AMTICO INTERNATIONAL 25 rue de Sèvres 92100 BOULOGNE FRANCE	RL 2014/493-1	NF EN ISO 9239-1
		RL 2014/493 -2	NF EN ISO 11925-2

**3.2. Tests results**

Test method	Product	Number of tests	Results	
			Parameters	Compliance parameters
NF EN ISO 11925-2	AMTICO CLICK SU5W3002 with underlay “UNDERLAY 19”	6	Fs ≤ 150 mm	Compliant
Surface exposure-15 secondes			Ignition of the filter paper	Compliant

3.3. Tests results

Test method	Product	Number of tests	Parameters	Results
				Continuous parameters : mean value
NF EN ISO 9239-1	AMTICO CLICK SU5W3002 with underlay "UNDERLAY – 19"	3	Critical heat flux (kW/m <sup>2</sup> )	10,0
			Smoke (% X min)	522,7

4. Classification and field of application4.1. Reference of classification

This classification has been carried out in accordance with EN 13501-1 :2007 & A1 (2013).

4.2. Classification

Fire behaviour		Smoke production
B <sub>fl</sub>	-	s1

**Classification : B<sub>fl</sub> – s1**

4.3. Field of application

This classification is valid for the following end use applications :

Loose laid a wood panel particle board without flame retarded classified C<sub>fl</sub>-s1, with a density  $\geq 510 \text{ kg/m}^3$  and over a fibre-cement A2<sub>fl</sub> or A1<sub>fl</sub> class with a density  $\geq 1350 \text{ kg/m}^3$ .

This classification is valid for the following product parameters :

AMTICO CLICK SU5W3002:

- A nominal mass per unit area of: 8400 g/m<sup>2</sup>
- A nominal thickness of : 5,0 mm
- A nominal wear layer of: 0,55 mm

Underlay "UNDERLAY – 19":

- A nominal mass per unit area : 100 g/m<sup>2</sup>
- A nominal thickness : 1,0 mm
- Nominal Density : 100 kg/m<sup>3</sup>

## 5. Limitations


This classification document does not represent type approval or certification of the product.

“The classification assigned to the product in this report is appropriate to a declaration of conformity by the manufacturer within the context of system 3 attestation of conformity and CE marking under the Construction Products Directive.

The manufacturer has made a declaration, which is held on file. This confirms that the products design requires no specific processes, procedures or stages (no addition of flame-retardants, limitation of organic content, or addition of fillers) that are aimed at enhancing the fire performance in order to obtain the classification achieved. As a consequence the manufacturer has concluded that system 3 attestation is appropriate.

The test laboratory has, therefore, played no part in sampling the product for the test, although it holds appropriate references, supplied by the manufacturer, to provide for traceability of the samples tested.”

The Responsible for the Test  
David VANDIERDONCK

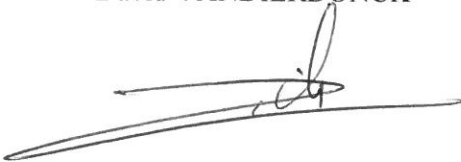

For the SARL C.R.E.T.  
The Technical Director  
Marc WELCOMME



*End of the classification report*